

# ANALYSIS DISTRIBUTION OF THE EQUIVALENT PLASTIC STRAIN, CONTACT PRESSURE AND TEMPERATURE DURING THE METAL TUBES EXTRUSION

Petru Paul DINCU<sup>1</sup>, Gheorghe ACHIMAȘ<sup>1</sup>, Adriana NEAG<sup>1</sup> and Adrian TRIF<sup>1</sup>

<sup>1</sup> Technical University of Cluj-Napoca, Machine Building Faculty, Bd. Muncii 103105, România

E-mail: pauldincu@yahoo.com; gheorghe.achimas@tcm.utcluj.ro; adriana.neag@ipm.utcluj.ro; adrian.trif@tcm.utcluj.ro

**ABSTRACT:** Numerical simulation of tubes extrusion processes has become an important tool to improve these processes. In this work, the cold extrusion tubes from a low carbon steel C15 was simulated by FEM with the commercial software DEFORM-2D. The objective of this study is to predict the distribution of the equivalent plastic strain, of the contact pressure and of the temperature on the work surfaces of the punch and on the extrusion die. The tubes extrusion process was also simulated using the commercial software FORGE® 3D and here are present the flow-line pattern which are symmetrical and clearly dependent of the geometry.

**KEYWORDS:** distribution of the equivalent plastic, heat distribution, evolution of the vertical force in reverse extrusion.

## 1. INTRODUCTION

The technological process of cold reverse extrusion of low carbon steels is applied with maximum efficiency to small parts produced in large batches using specialized manufacturing equipment.

The interest shown by specialists for the cold extrusion of concave steel products having a small diameter has constantly increased, the proof being the large number of papers dealing with this topic published in scientific magazines.

The quality of the tubular parts with small diameter manufactured through extrusion must be assessed both through the dimensional accuracy and the deviation from the ideal configuration. One cannot neglect the roughness of the inner and outer surfaces achieved after the extrusion process and the modification of the mechanical properties of the workpiece material as a result of the hardening induced during the cold extrusion process.

Extrusion is one of the main methods of forming in which materials are forced to fill through a die, to obtain a specific shape of constant cross section.

Generally the extrusion process is used to produce cylindrical bars or hollow tubes or is used as a preparatory stage for drawn rod, or forged parts, in automobile, aircraft,


construction and other industries. There are several categories of extrusion process including forward, backward and radial.

## 2 EXTRUSION OF A STEEL TUBULAR PART. CASE STUDY

The shape and the dimensions of the part whose extrusion technology is the object of the case study are presented in Fig. 1. The manufacturing documentation specifies that the part is to be produced from a low carbon steel having the properties of a C15 steel (according to SR EN 10277-2: 2008). Due to its relative low content of carbon, the C15 steel is characterized by a very good formability, even in the conditions of cold extrusion process. In fact, this material is widely used in the domain of cold extrusion.

The part in Figure 1 can be manufactured through reverse extrusion. The dimensions of the cylindrical workpiece being extruded were established using the equivalent mass method. For verifying the cold extrusion possibility the process of plastic deformation was numerically simulated. The finite element analysis program DEFORM-2D [1] was used for this purpose.



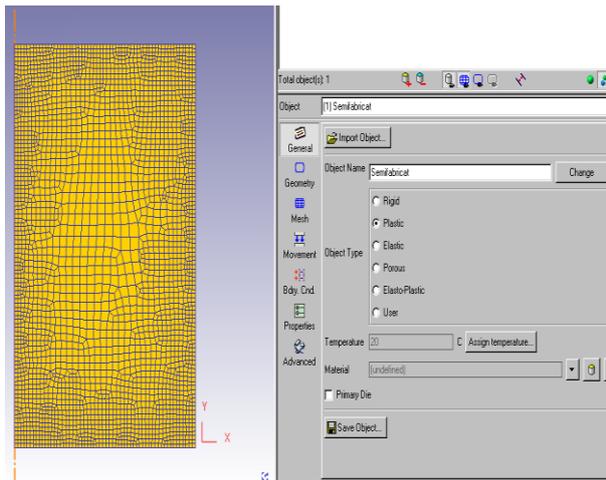

**Figure 3. Import of the geometrical model of the workpiece, its finite element meshing and specification of the associated mechanical model**

- The import of the geometrical model of the workpiece, its finite element meshing and specification of associated mechanical models (see Figure 3). Due to the cylindrical symmetry of the extrusion process, the geometries of the workpiece and tools that produce the deformation are described by means of axial sections. These sections were modelled using the AutoCAD design program and transferred to the DEFORM-2D program as DXF files. The workpiece was meshed into about 3000 finite elements, DEFORM-2D being allowed to refine the mesh during the simulation if needed. The mechanical model associated to the workpiece is of elastoplastic type.
- Specifying the kinematic restrictions for the finite element mesh associated to the workpiece: locking the radial translations of the nodes situated on the vertical symmetry axis of the extrusion process.
- Import of the geometrical model of the tools, their meshing into finite elements and specifying the associated mechanical model. The tools were meshed into about 1000 finite elements, a mesh that DEFORM-2D program is not allowed to refine during the simulation. The mechanical model associated to the tools is of rigid type.
- Specifying the control parameters of the punch motion: direction of motion (the negative direction of axis Y) and the translation speed (17.4 mm/sec)
- Locking the extrusion die movement.
- Specifying the material being extruded, in this case, C15 steel selected from the library of the DEFORM-2D program
- Specifying the material of the punch and the extrusion die: toolmaking steel DIN-D5 selected from the library of the DEFORM-2D program. DIN-D5 steel is widely used for the cold extrusion dies [2, 3, 4]. After heat treatment this material achieves a hardness of about 55 HRC.
- Specifying the boundaries along which there is heat exchange between the workpiece and tools, the workpiece and environment and the tools and environment. The heat transfer determines significant variations of the workpiece and tools temperature having important influences on the intensity of the wearing phenomena.
- Specifying the heat transfer coefficient – average value selected according to the recommendations of the DEFORM-2D preprocessor.
- Specifying the parameters that define the frictional contact model between the workpiece and tools.
- Specifying the parameters that define the tool wearing process model. For the numerical simulation of the cold deformation processes, the DEFORM-2D [1] program documentation recommends using the Archard wearing model. In its more general variant, this model defines the volume of material  $W$  lost by a tool by wear in the time interval  $[0, T]$  the formula

$$W = \int_0^T K \frac{p^a v^b}{H^c} dt \quad (1)$$

where  $p$  is the pressure on the contact surface,  $v$  is the relative sliding speed of the workpiece on the tool surface,  $H$  is the Rockwell hardness of the tool, and  $K, a, b,$  and  $c$  are constants that depend on the couple of materials in contact. For the couple of materials steel-steel, the DEFORM-2D [1] documentation recommends using of the

following values:  $K = 10^{-9}$ ,  $a = 1$ ,  $b = 1$ , and  $c = 1$ .

- Specifying the Rockwell hardness of the tool material: 55 HRC, value achieved by the steel DIN-D5 after heat treatment.

#### 4. SIMULATION RESULTS

To facilitate the interpretation of the numerical results DEFORM-2D provides the users with a graphical postprocessor. Generally, the simulation results are presented as colored maps accompanied by a legend that associates each color field a value range of the analyzed result. Among the most useful information items provided by DEFORM-2D the following ones can be mentioned:

- Distribution of the equivalent plastic strain accumulated in the workpiece during the extrusion process (Figure 4.a)
- Distribution of the damage risk indicator in the final stage of the extrusion (Figure 4.b)
- Distribution of the contact pressure on the work surfaces of the punch (Figure 5.a), and die (Figure 5.b) in the final stage of the extrusion process
- Distribution of the temperature in the axial section of the workpiece (Figure 6.a), punch (Figure 6.b), and die (Figure 6.c) in the final stage of the extrusion process
- Thickness of the material layer lost due to wearing by the punch (Figure 7.a), and die (Figure 7.b) for each extruded part (estimation given by Archard's law)
- Diagram showing the evolution of the vertical force developed by the punch during the extrusion process (Figure 8).

The equivalent plastic strain reflects the level of the strain hardening of the material. The diagram in picture 4.a presents the distribution of this value in the final stage of the extrusion process. As it can be observed in the diagram legend, the maximum value of the equivalent plastic strain is 4.9, being found in the region where the workpiece suffers the strongest distortion (at the joint between the cylindrical wall and the bottom area of the part). It can be also observed that the equivalent plastic strain

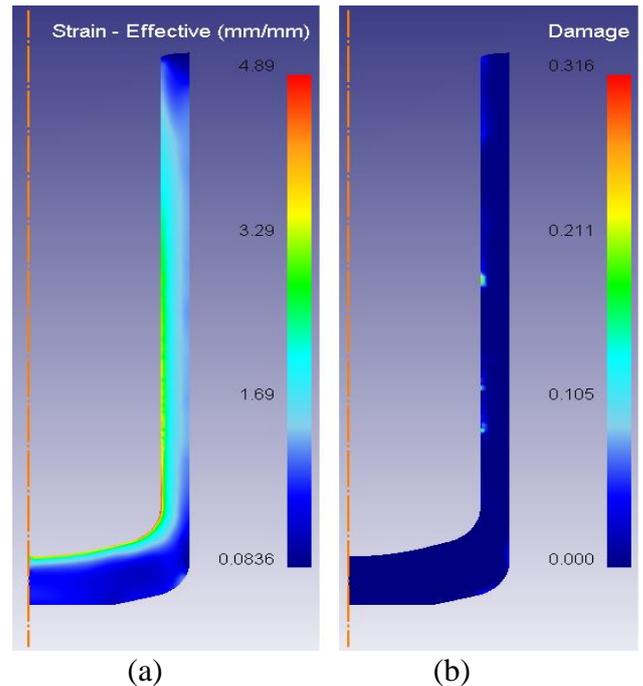


Figure 4. Distribution of the equivalent plastic strain (a) and damage indicator that highlights the exceeded value of the forming capability of the workpiece (b) in the final stage of the extrusion process

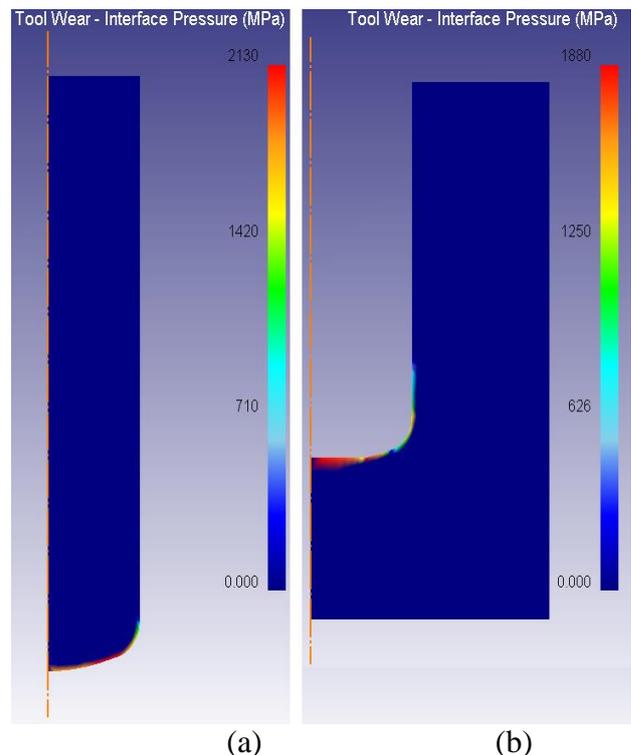


Figure 5. Distribution of the contact pressure on the work surfaces of the punch (a), and extrusion die (b) in the final stage of the forming process

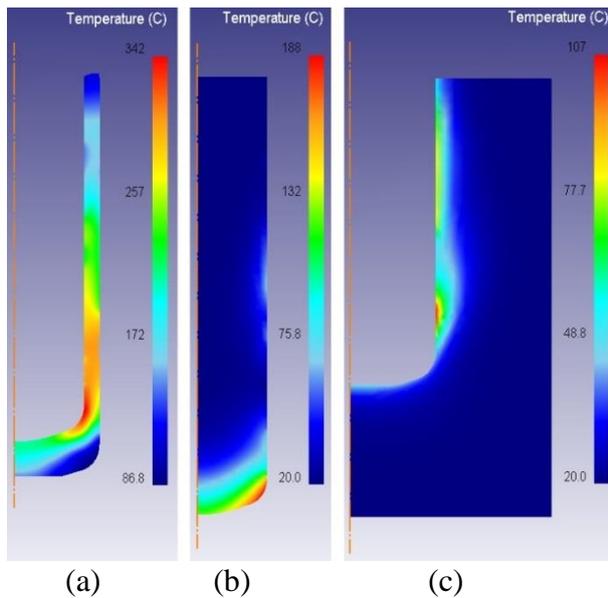


Figure 6. Distribution of the temperature in the axial section of the workpiece (a), punch (b), and extrusion die (c) in the final stage of the forming process

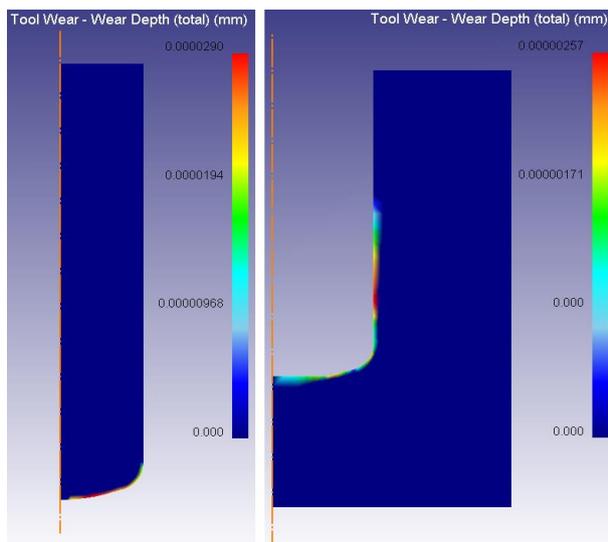


Figure 7. Thickness of the material layer lost due to wearing by the punch (a) and die (b) for each extruded part (estimation given by Archard's law)

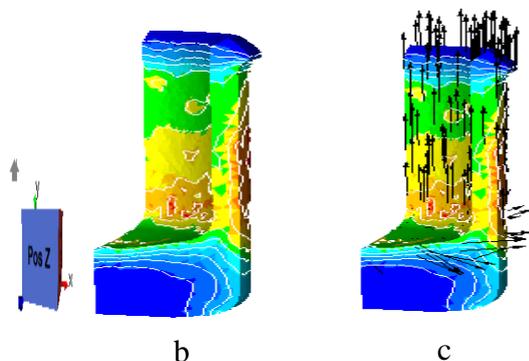


Figure 9. Deformation distribution in the extruded tube after a 28 mm piston stroke; b) and c) C15.

has large values on the frontal side of the punch, and also on the inner part of the cylindrical wall. This situation is the consequence of the strain gradually accumulated during the deformation of the workpiece by the punch and material compression against the cylindrical wall. Although the level of the plastic strain is high, it is still in the admissible range for the C15 steel. This fact results from the diagram shown

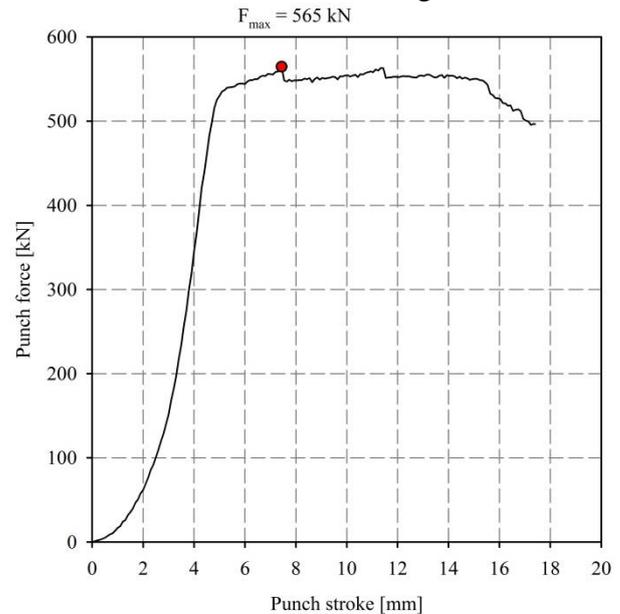


Figure 8. Evolution of the vertical force developed by the punch during the extrusion process

in Figure 4.b, according to which the risk indicator reaches nowhere in the axial section of the extruded part values larger than one.

### 5. DETERMINING EQUIVALENT DEFORMATIONS

The metal tubes extrusion process involves high deformations and serious changes of the direction of deformation. Another aim of this study is to determine the distribution of equivalent deformations in the C15 extruded tubes. Figure 9 presents the uneven distribution of deformations in the extruded tube after a 28 mm piston stroke, under the same lubrication circumstances (coefficient of friction  $\mu = 0.2$ ).

When analyzing the values of the equivalent deformation we can see that it is not even and that it has local maximum values.

The equivalent deformation records maximum values in the area of the outer

vertical wall of the tube and respectively on the inner wall, above the connection radius (i.e. in the area where the punch first enters the material). As the punch advances, the travel on the y direction increases and the punch deforms also areas of undeformed material, areas where deformations are lower. In order to better understand how deformations are distributed during the tube extrusion process Figure 9 c) presents vectorially the C15 extruded tube.

## 6. CONCLUSIONS

As previously mentioned, the wear of the extrusion tools is highly influenced by the pressure level on the contact surfaces with the workpiece, and also by the temperature. The diagrams in Figure 5 show the distribution of the contact pressure on the active surfaces of the punch and die at the end of the extrusion process. It can be noticed the extremely high pressure levels both on the frontal side of the punch (a maximum of 2130 MPa), and on the bottom side of the die cavity (a maximum of 1880 MPa). The temperature also registers a significant growth during the extrusion process. According to the diagrams in Figure 6, the workpiece suffers the strongest heating (a maximum of 342 °C). On the second place is the punch whose temperature reaches a maximum of 188 °C at the joint of the cylindrical wall with the frontal side. The element that suffers the less heating is the extrusion die whose maximum temperature is 107 °C. It can be deduced that the wear of the punch will be more aggressive. This fact is confirmed by the diagrams in Figure 7, that show the thickness of the material layer lost due to wearing by the punch and die for each extruded part. One may also notice that the areas where the wear is more aggressive are the same with those where the mechanical and heat loads acting on tools are higher. The diagram in Figure 8 presents the evolution of the vertical

force developed by the punch during the extrusion process. The vertical force acting on the die has a similar evolution, because, according to the principle of reciprocal actions, it is equal in absolute value and of opposite sign to the force developed by the punch. The diagram in Figure 8 highlights a quite fast growing of the force to a maximum level of 565 kN, after which the force remains practically unchanged. The evolution up to the maximum value corresponds to the incipient stage of the extrusion process and continues until the cylindrical wall of the part begins to take shape. The horizontal level in the diagram in Figure 8 corresponds to a stable phase of the extrusion process, when the cylindrical wall continues its growing in the space between the punch and the die. Manufacturing tubes by extrusion in low friction conditions process will reduce the forming load and energy and therefore, will increase the productivity of the production process. In each of the cases presented in figure 9, the value of the equivalent deformation decreases on a radial direction, from the inner part of the tube towards its outer side. On the direction of the y-axis, the equivalent deformation is low in the upper part of the tube and at its bottom as well (the area where the material is pressed). The difference between the minimum and maximum equivalent deformation values is over 180%.

## 7. REFERENCES

- [1] <http://www.deform.com/products/deform-2d/2d-brochure.pdf>.
- [2] Lange, K. *Handbook of Metal Forming*. Dearborn: Society of Mechanical Engineers, 2006.
- [3] Lange, K., Kammerer, M., Pöhlandt, K., Schöck, J. *Fließpressen. Wirtschaftliche Fertigung metallischer Präzisionswerkstücke*. Berlin: Springer, 2008.
- [4] Schuler Gmbh (ed.) *Metal Forming Handbook*. Berlin: Springer, 1998